

# A green and efficient oxidation of alcohols by supported gold catalysts using aqueous H<sub>2</sub>O<sub>2</sub> under organic solvent-free conditions†

Ji Ni, Wen-Jian Yu, Lin He, Hao Sun, Yong Cao,\* He-Yong He and Kang-Nian Fan

Received 12th November 2008, Accepted 6th March 2009

First published as an Advance Article on the web 13th March 2009

DOI: 10.1039/b820197h

The use of supported gold nanoparticles as an efficient, green and reusable catalyst for the oxidation of various alcohols to the corresponding carbonyl compounds using aqueous hydrogen peroxide as an environmentally benign oxidant is presented. The reaction proceeds with good to excellent yields in particular for nonactivated alcohols under base-free conditions.

Oxidation of alcohols to their corresponding carbonyl compounds is one of the most important processes for production of fine and specialty chemicals.<sup>1</sup> Traditional methods involve use of toxic and expensive stoichiometric metal oxidants, such as chromate and permanganate,<sup>2</sup> or harmful organic solvents,<sup>3</sup> or require vigorous reaction conditions.<sup>4</sup> From both the environmental and economic points of view, there is a strong incentive to develop a green, economic and efficient alcohol oxidation process.<sup>5</sup> In this context, much recent attention has been directed toward the aerobic oxidation of alcohols with reusable heterogeneous solid catalysts in aqueous media under mild conditions,<sup>6</sup> which is particularly suitable for industrial practices. However, very few catalysts are sufficiently active for nonactivated alcohols, like aliphatic and alicyclic alcohols.<sup>7</sup> In particular, bases such as KOH or K<sub>2</sub>CO<sub>3</sub> are frequently needed for oxidation of primary aliphatic alcohols (e.g. 1-octanol) in water,<sup>8</sup> which is clearly not green and presents notorious problems such as corrosion and waste base treatment. In this respect, the development of a novel catalytic system that exhibits a wide range of substrate tolerance under mild and base-free aqueous conditions still remains a major challenge.

Supported gold catalysts have attracted tremendous recent attention owing to their unique catalytic properties for a broad array of organic transformations,<sup>9</sup> especially for aerobic oxidation of alcohols under mild conditions.<sup>6c,d,9a,10–12</sup> Over the last few years, our group,<sup>11</sup> Kobayashi *et al.*<sup>6c</sup> and Corma *et al.*<sup>12</sup> reported that Au nanoclusters deposited on metal oxides or polymers are highly effective for aerobic oxidation of various alcohols. In general, organic solvents and/or bases are necessary to achieve high yield and selectivity.<sup>11</sup> The oxidation of alcohols under solvent- and base-free conditions was reported,<sup>12,13</sup> the yield of target product was, however, much lower than that obtained with organic solvent and/or base conditions. Herein,

we report the development of a new efficient H<sub>2</sub>O<sub>2</sub>–Au system exhibiting significantly enhanced activity for the oxidation of alcohols under base-free aqueous conditions. Hydrogen peroxide (H<sub>2</sub>O<sub>2</sub>), previously established to be an ideal oxidant for the green oxidation of alcohols with homogeneous metal peroxo complexes,<sup>14</sup> has shown to be particularly effective for gold catalyzed selective oxidation of nonactivated alcohols. To the best of our knowledge, this study also forms the first hectogram-scale clean synthesis of aliphatic acids using gold catalysts.

First of all, 1-phenylethanol was used as a model substrate to study the catalytic activity of the different supported gold catalysts. The results of these studies (Table 1) show that gold supported on carbon leads to very low conversion (ca. 12%). The Au/Fe<sub>2</sub>O<sub>3</sub> and Au/Al<sub>2</sub>O<sub>3</sub> catalysts show moderate activity (ca. 34–37%), while Au/TiO<sub>2</sub> supplied by the World Gold Council and Au/CeO<sub>2</sub> give a higher conversion value (ca. 58–62%), gold supported on TiO<sub>2</sub> supplied by Mintek afford the highest conversion (ca. 99%), with yields of isolated product of between 98 and 100%.‡ No conversion was found in the absence of catalyst or the use of Au-free TiO<sub>2</sub> catalysts under similar reaction conditions. Additional examination of the relationship between the alcohol oxidation activities and a series of Mintek Au/TiO<sub>2</sub> catalysts calcined at elevated temperatures (Fig. S1–4 in ESI)† revealed that use of smaller Au nanoparticles gave higher activity, as shown in Fig. 1. This result, together with the fact that the small Au NPs can substantially facilitate the crucial H<sub>2</sub>O<sub>2</sub> decomposition,<sup>15</sup> strongly suggests that the high dispersion of Au NPs in combination with a beneficial synergetic interaction with the TiO<sub>2</sub> support is the key factor


**Table 1** Oxidation of 1-phenylethanol by aqueous H<sub>2</sub>O<sub>2</sub> <sup>a</sup>

Entry	Catalyst	Conversion (%)
1 <sup>b</sup>	0.8% Au-C (WGC)	12
2	4.5% Au-Fe <sub>2</sub> O <sub>3</sub> (WGC)	34
3	1.5% Au-TiO <sub>2</sub> (WGC)	62
4	0.9% Au-Al <sub>2</sub> O <sub>3</sub> (Mintek)	37
5	1% Au-TiO <sub>2</sub> (Mintek)	99
6	1% Au-CeO <sub>2</sub>	58

<sup>a</sup> Reaction conditions: 10 mmol 1-phenylethanol, 10 mL H<sub>2</sub>O, 90 °C, 5% H<sub>2</sub>O<sub>2</sub> added dropwise, substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:150:1. <sup>b</sup> This sample catalyst was used as-received. According to the characterizations of the Au/C sample provided by the World Gold Council, the water content of the Au/C reference catalyst was equal to 40%.

Department of Chemistry & Shanghai Key Laboratory of Molecular Catalysis and Innovative Material, Fudan University, Shanghai, 200433, P. R. China. E-mail: yongcao@fudan.edu.cn; Fax: (+86-21) 65642978; Tel: (+86-21) 55665287


† Electronic supplementary information (ESI) available: Experimental section, TEM and XPS data. See DOI: 10.1039/b820197h

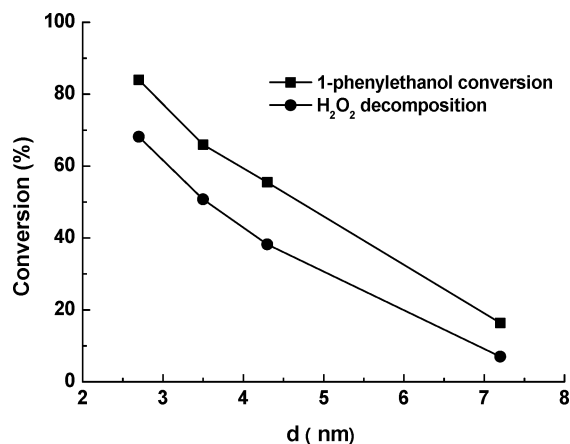

**Fig. 1** 1-Phenylethanol conversion and H<sub>2</sub>O<sub>2</sub> decomposition versus gold particle dimension; oxidation of 1-phenylethanol: 10 mmol 1-phenylethanol, Au/TiO<sub>2</sub> (Mintek), 10 mL H<sub>2</sub>O, 90 °C, 5% H<sub>2</sub>O<sub>2</sub> added dropwise, substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:110:1; H<sub>2</sub>O<sub>2</sub> decomposition: 1.5 wt% H<sub>2</sub>O<sub>2</sub> aqueous solution 10 mL, Au/TiO<sub>2</sub> (Mintek) 80 mg, 25 °C for 80 min in open air. The rate of decomposition was calculated based on the amount of H<sub>2</sub>O<sub>2</sub> remaining, which was measured by the titration of 0.1 M Ce(SO<sub>4</sub>)<sub>2</sub> with 1.5 w/v% ferroin solution as an indicator.

for achieving high activity in the H<sub>2</sub>O<sub>2</sub>-mediated oxidation of alcohols.

The Mintek Au/TiO<sub>2</sub> catalyst was stable and can be easily reused in the oxidation of 1-phenylethanol. After the first alcohol oxidation, the catalyst was separated from the reaction mixture by filtration, thoroughly washed with water, and then reused as catalyst for the next run under the same conditions. As shown in Fig. 2, the acetophenone yields remained essentially constant for the five successive cycles, reflecting the high stability and reusability of the catalyst. This was consistent with the characterization results for this catalyst. TEM and XPS results (Fig. S5 and S7 in ESI)<sup>†</sup> showed essentially no changes in the mean diameters of the Au nanoparticles and in the metallic state of Au, respectively, after the five successive runs. Moreover, it was confirmed by induced coupled plasma (ICP) techniques that the Au content of the used Au/TiO<sub>2</sub> catalyst was the same as that of the fresh catalyst and that no Au was in the filtrate.

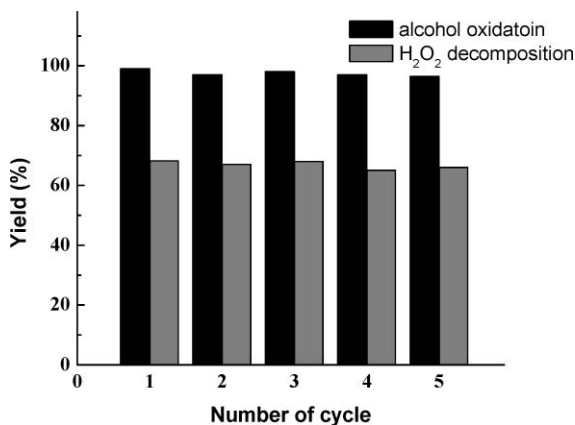

**Fig. 2** Recycling of the Mintek Au/TiO<sub>2</sub> catalyst for the oxidation of 1-phenylethanol: 10 mmol substrate, 10 mL H<sub>2</sub>O, 90 °C, 5% H<sub>2</sub>O<sub>2</sub> added dropwise. Substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:150:1. For comparison, the corresponding H<sub>2</sub>O<sub>2</sub> decomposition rates are also included.

**Table 2** Oxidation of non-activated alcohols by aqueous H<sub>2</sub>O<sub>2</sub><sup>a</sup>

Entry	Substrate	Product	Conv. (%)	Sel. (%)
1			87	100
2			98	100
3			>99	100
4 <sup>b</sup>			>99	100
5 <sup>b</sup>			>99	>99
6 <sup>b</sup>			>99	90 <sup>c</sup>













<sup>a</sup> Reaction conditions: 10 mmol Substrate, 10 mL H<sub>2</sub>O, 90 °C, 5% H<sub>2</sub>O<sub>2</sub> added dropwise, substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:150:1. <sup>b</sup> Substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:250:1. <sup>c</sup> Octyl octanoate was found as by-product.

To examine the scope of the alcohol reaction with the H<sub>2</sub>O<sub>2</sub>-Au/TiO<sub>2</sub> system, we extended our studies to various structurally different alcohols. The results are summarized in Table 2. It was found that primary and secondary alcohols were oxidized to the corresponding carboxylic acids and ketones, respectively. Notably, H<sub>2</sub>O<sub>2</sub>-Au/TiO<sub>2</sub> was capable of catalyzing the oxidation of various nonactivated alcohols. For alicyclic alcohols and secondary aliphatic alcohols, *i.e.* 2-octanol, they gave ketones in excellent yields of 87–98% (Table 2, entries 1–2). Moreover, it was found that the chemoselective oxidation of allylic alcohols having a terminal double bond, such as 1-hexene-3-ol, also proceeded efficiently (Table 2, entry 3). Contrastingly, a previously reported H<sub>2</sub>O<sub>2</sub>-Pt black system is found to be totally inactive for this substrate, owing to a strong coordination of the –C=CH<sub>2</sub> group to the Pt<sup>0</sup> complex.<sup>16</sup> It is especially noteworthy that H<sub>2</sub>O<sub>2</sub>-Au/TiO<sub>2</sub> was highly active for the oxidation of primary aliphatic alcohols, the most inactive alcohols, in the absence of any bases (Table 2, entries 4–6). For example, the yield of 1-hexanoic acid in 1-hexanol oxidation was as high as 99% at a 100% conversion.

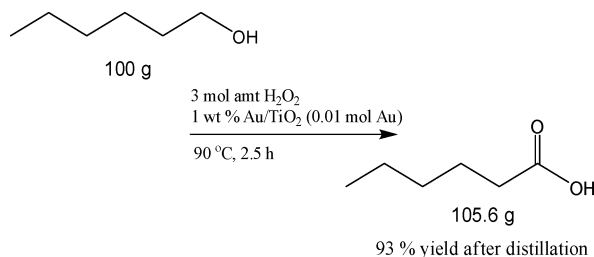
Furthermore, it was found that the H<sub>2</sub>O<sub>2</sub>-mediated oxidations also proceeded smoothly in a hectogram-scale synthesis to give a high yield of formation of the corresponding carboxylic acids. As shown in Scheme 1, by stirring a mixture of 1-hexanol (100 g) in the presence of a 0.01 molar amount of Au catalyst and 3.0 molar amount of aqueous H<sub>2</sub>O<sub>2</sub> (5%) for 2.5 h, 1-hexanoic acid could be obtained in a 93% yield (105.6 g). Notably, this is the first example of a hectogram-scale clean oxidation of alcohols under base-free conditions in neat water using a heterogeneous gold catalysts.

Activated alcohols, such as benzylic alcohols, were also oxidized at 90 °C with H<sub>2</sub>O<sub>2</sub> in the presence of Au/TiO<sub>2</sub> to give the corresponding carbonyl compounds in good to excellent yields (Table 3). Like most of the catalysts reported

**Table 3** Oxidation of activated alcohols by aqueous H<sub>2</sub>O<sub>2</sub><sup>a</sup>

Entry	Substrate	Product	Conv. (%)	Sel. (%)
1 <sup>b</sup>			>99	100
2			>99	85 <sup>c</sup>
3			>99	44 <sup>c</sup>
4			>99	61 <sup>c</sup>
5			>99	37.5 <sup>c</sup>
6 <sup>b</sup>			>99	100

<sup>a</sup> Reaction conditions: 10 mmol substrate, 10 ml H<sub>2</sub>O, 90 °C, 5% H<sub>2</sub>O<sub>2</sub> added dropwise, substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:250:1. <sup>b</sup> Substrate:H<sub>2</sub>O<sub>2</sub>:Au = 100:150:1. <sup>c</sup> Aldehyde was found as by-product.

**Scheme 1** Hectogram-scale oxidation of 1-hexanol.

previously,<sup>6–12</sup> Au/TiO<sub>2</sub> efficiently catalyzed the oxidation of secondary aromatic alcohol, such as 1-phenylpropanol (Table 3, entry 1), almost quantitatively to their target products (~99% yields). Benzyl alcohol was oxidized to benzoic acid at a 100% conversion, although with a selectivity of only 85% (Table 3, entry 2; the other product was mainly benzaldehyde). Benzyl alcohols with electron-donating groups were also successfully oxidized, in which a shift in selectivity from acids to benzaldehydes was observed (Table 3, entries 3–5). It is worth noting that chemoselective oxidation of cinnamyl alcohol with the sole formation of cinnamaldehyde could be accomplished (Table 3, entry 6). Interestingly, an epoxidized compound of cinnamyl alcohol was not observed. All these results clearly showed the efficiency of the H<sub>2</sub>O<sub>2</sub>–Au/TiO<sub>2</sub> system in the oxidation of both activated and nonactivated alcohols in water.

Attempting to gain insight into the origin of the enhanced activity achieved by using aqueous H<sub>2</sub>O<sub>2</sub> as oxidant is important. Although an extensive mechanistic study has not yet been

conducted, it is known that the  $\alpha$ -hydrogen abstraction of an alcohol may be involved in the rate determining step based on the isotope kinetic study ( $k_{\text{H}}/k_{\text{D}} = 1.7\text{--}2.0$ ).<sup>17</sup> In addition, H<sub>2</sub>O<sub>2</sub> was found to be indispensable for the reaction progress as inferred by the data in Fig. 1, which prompted us to propose a possible mechanism of the present H<sub>2</sub>O<sub>2</sub>–Au-mediated alcohol oxidation, as illustrated in Fig. S8 (ESI).<sup>†</sup> The key aspect of H<sub>2</sub>O<sub>2</sub> is to facilitate the abstraction of the  $\alpha$ -hydrogen as a hydrogen scavenger, leading to the formation of a meta-alcoholate species during the initial step of the reaction. The Au-alcoholate complex may be further attacked by H<sub>2</sub>O<sub>2</sub> or the Au-hydridoperoxide complex generated from the reaction of Au<sup>0</sup> with H<sub>2</sub>O<sub>2</sub>, to form the final carbonyl compound *via* a  $\beta$ -elimination pathway. The overall effect is that a dramatically boosted activity for alcohol oxidation is achieved in contrast to the normal aerobic process in which dioxygen or air was used as the oxidant.

In summary, we have demonstrated that the Au/TiO<sub>2</sub> catalyst has great potential for the environmentally benign oxidation of alcohols with aqueous hydrogen peroxide under mild and organic solvent-free conditions. The H<sub>2</sub>O<sub>2</sub>–Au/TiO<sub>2</sub> protocol has been proven to be particularly efficient in the oxidative transformation of nonactivated alcohols in aqueous media. The stability of the catalyst has also been demonstrated convincingly by conducting five successive runs without a significant drop in the reaction rate. Further extension of the present H<sub>2</sub>O<sub>2</sub>–Au catalytic system to many other key oxidative transformations is currently being explored.

## Acknowledgements

Financial support by the National Natural Science Foundation of China (20633030, 20721063 and 20873026), the National Basic Research Program of China (2003CB 615807), Shanghai Education Committee (06SG03) and Science & Technology Commission of Shanghai Municipality (08DZ2270500, 07QH14003) is kindly acknowledged.

## Notes and references

<sup>†</sup> Without the use of H<sub>2</sub>O<sub>2</sub> (under an air atmosphere), acetophenone was obtained in only <10% yield over the Mintek Au/TiO<sub>2</sub> catalyst.

- R. A. Sheldon and J. K. Kochi, *Metal-Catalyzed Oxidation of Organic Compounds*, Academic Press, New York, 1981.
- W. J. Mijs and C. R. H. de Jonge, *Organic Synthesis by Oxidation with Metal Compounds*, Plenum Press, New York, 1986.
- (a) Z. Hou, N. Theyssen, A. Brinkmann and W. Leitner, *Angew. Chem., Int. Ed.*, 2005, **44**, 1346; (b) B. Z. Zhan, M. A. White, T. K. Sham, J. A. Pincock, R. J. Doucet, K. V. R. Rao, K. N. Robertson and T. S. Cameron, *J. Am. Chem. Soc.*, 2003, **125**, 2195; (c) B. T. Guan, D. Xing, G. X. Cai, X. B. Wan, N. Yu, Z. Fang and Z. J. Shi, *J. Am. Chem. Soc.*, 2005, **127**, 18004.
- (a) C. X. Zhang, P. Chen, J. Liu, Y. H. Zhang, W. Shen, H. L. Xu and Y. Tang, *Chem. Commun.*, 2008, 3290; (b) J. Shen, W. Shan, Y. H. Zhang, J. M. Du, H. L. Xu, K. N. Fan, W. Shen and Y. Tang, *Chem. Commun.*, 2004, 2880.
- T. Mallat and A. Baiker, *Chem. Rev.*, 2004, **104**, 3037.
- (a) Y. Uozumi and R. Nakao, *Angew. Chem., Int. Ed.*, 2003, **42**, 194; (b) Y. M. A. Yamada, T. Arakawa, H. Hocke and Y. Uozumi, *Angew. Chem., Int. Ed.*, 2007, **46**, 704; (c) H. Tsunoyama, H. Sakurai, Y. Negishi and T. Tsukuda, *J. Am. Chem. Soc.*, 2005, **127**, 9374; (d) H. Miyamura, R. Matsubara, Y. Miyazaki and S. Kobayashi, *Angew. Chem., Int. Ed.*, 2007, **46**, 4151; (e) K. Mori, T. Hara, T. Mizugaki, K. Ebitani and K. Kaneda, *J. Am. Chem. Soc.*, 2004, **126**, 10657.

- 7 T. Wang, C. X. Xiao, L. Yan, L. Xu, J. Luo, H. Shou, Y. Kou and H. C. Liu, *Chem. Commun.*, 2007, 4375.
- 8 (a) X. Wang, H. Kawanami, N. M. Islam, M. Chatterjee, T. Yokoyama and Y. Ikushima, *Chem. Commun.*, 2008, 4442; (b) H. Tsunoyama, T. Tsukuda and H. Sakurai, *Chem. Lett.*, 2007, **36**, 212; (c) G. ten Brink, I. W. C. E. Arends and R. A. Sheldon, *Science*, 2000, **287**, 1636; (d) B. P. Buffin, J. P. Clarkson, N. L. Belitz and A. Kundu, *J. Mol. Catal. A: Chem.*, 2005, **225**, 111.
- 9 (a) L. Prati and M. Rossi, *J. Catal.*, 1998, **176**, 552; (b) A. Corma and P. Serna, *Science*, 2006, **313**, 332; (c) C. H. Christensen, B. Jorgensen, J. RassHansen, K. Egeblad, R. Madsen, S. K. Klitgaard, S. M. Hansen, M. R. Hansen, H. C. Andersen and A. Riisager, *Angew. Chem., Int. Ed.*, 2006, **45**, 4648; (d) F. Z. Su, L. He, J. Ni, Y. Cao, H. Y. He and K. N. Fan, *Chem. Commun.*, 2008, 3531; (e) J. E. Bailie and G. J. Hutchings, *Chem. Commun.*, 1999, 2151; (f) T. Hayashi, K. Tanaka and M. Haruta, *J. Catal.*, 1998, **178**, 566; (g) A. K. Sinha, S. Seelan, S. Tsubota and M. Haruta, *Angew. Chem., Int. Ed.*, 2004, **43**, 1546.
- 10 (a) S. Carrettin, P. McMorn, P. Johnston, K. Griffin and G. J. Hutchings, *Chem. Commun.*, 2002, 696; (b) N. F. Zheng and G. D. Stucky, *Chem. Commun.*, 2007, 3862; (c) P. Haider and A. Baiker, *J. Catal.*, 2007, **248**, 175; (d) C. Burato, P. Centomo, G. Pace, M. Favaro, L. Prati and B. Corain, *J. Mol. Catal. A: Chem.*, 2005, **238**, 26; (e) D. I. Enache, J. K. Edwards, P. Landon, B. Solsona-Espriu, A. F. Carley, A. A. Herzing, M. Watanabe, C. J. Kiely, D. W. Knight and G. J. Hutchings, *Science*, 2006, **311**, 362.
- 11 (a) F. Z. Su, Y. M. Liu, L. C. Wang, Y. Cao, H. Y. He and K. N. Fan, *Angew. Chem., Int. Ed.*, 2008, **47**, 334; (b) L. C. Wang, L. He, Q. Liu, Y. M. Liu, M. Chen, Y. Cao, H. Y. He and K. N. Fan, *Appl. Catal., A*, 2008, **344**, 150; (c) L. C. Wang, Y. M. Liu, M. Chen, Y. Cao, H. Y. He and K. N. Fan, *J. Phys. Chem. C*, 2008, **112**, 6981.
- 12 (a) A. Abad, P. Concepcion, A. Corma and H. Garcia, *Angew. Chem., Int. Ed.*, 2005, **44**, 4066; (b) A. Abad, C. Almela, A. Corma and H. Garcia, *Tetrahedron*, 2006, **62**, 6666.
- 13 D. I. Enache, D. W. Knight and G. J. Hutchings, *Catal. Lett.*, 2005, **103**, 43.
- 14 (a) B. M. Trost and Y. Masuyama, *Tetrahedron Lett.*, 1984, **25**, 173; (b) O. Bortolini, V. Conte, F. Di Furia and G. Modena, *J. Org. Chem.*, 1986, **51**, 2661; (c) G. Barak, J. Dakka and Y. Sasson, *J. Org. Chem.*, 1988, **53**, 3553; (d) Y. Ishii, K. Yamawaki, T. Ura, H. Yamada, T. Yoshida and M. Ogawa, *J. Org. Chem.*, 1988, **53**, 35873; (e) R. Zennaro, F. Pinna, G. Strukul and H. Arzoumanian, *J. Mol. Catal.*, 1991, **70**, 269; (f) C. Venturello and M. Gambaro, *J. Org. Chem.*, 1991, **56**, 5924; (g) A. C. Dengel, W. P. Griffith and B. C. Parkon, *J. Chem. Soc., Dalton Trans.*, 1993, 2683; (h) R. Neumann and M. Gara, *J. Am. Chem. Soc.*, 1995, **117**, 5066.
- 15 The higher H<sub>2</sub>O<sub>2</sub> decomposition rate achieved for catalysts with smaller Au particle size can be attributed to the higher abundance of low-coordinated Au atoms, which are also believed to be the key sites for low temperature CO oxidation.
- 16 (a) Y. Kon, Y. Usui and K. Sato, *Chem. Commun.*, 2007, 4399; (b) Y. Kon, H. Yazawa, Y. Usui and K. Sato, *Chem.-Asian J.*, 2008, **3**, 1642.
- 17 A. Abad, A. Corma and H. Garcia, *Chem.-Eur. J.*, 2008, **14**, 2.