

Photooxygenation of Hydrocarbons over Efficient and Reusable Decatungstate Heterogenized on Hydrophobically Modified Mesoporous Silica

Lingli Ni,^a Ji Ni^b, Yuan Lv,^a Ping Yang,^{a*} and Yong Cao^{b*}

a Chemistry Department, East China Normal University, Shanghai, 200062, P.R. China,

b Laboratory of Molecular Catalysis and Innovative Materials,

Department of Chemistry, Fudan University, Shanghai 200433, P. R. China

Electronic Supplementary Information

1. Experimental details

1.1. Catalysts preparation

Mesoporous silica (SBA-15) was prepared following a literature procedure [Ref. S1] (pore diameter 6.7 nm, S_{BET} 757 $\text{m}^2\cdot\text{g}^{-1}$). 2 g Pluronic P123 triblock polymer ($\text{EO}_{20}\text{PO}_{70}\text{EO}_{20}$, $M_{\text{av}}=5800$, Aldrich) was dissolved in 65 mL deionized H_2O at room temperature stirred until fully dissolved, followed by adding 10 mL concentrated HCl (36.5%) solution and heated to 40 °C in a water bath. Then 4.5 mL TEOS was added dropwise in the homogeneous solution with stirring. This gel mixture was continuously stirred at 40 °C for 20 h, and finally hydrothermally treated in a Teflon-lined autoclave at 96 °C for 24 h in an oven. The solid product was separated by centrifuge, filtered, washed with deionized water, and dried in air at room temperature and calcined at 550 °C for 5 h.

The organo-grafting procedure was as follows [Ref. S2]: typically 1 g of the calcined SBA-15 powder refluxed with an excess amount of $\text{C}_n\text{H}_{2n+1}\text{Si}(\text{OC}_2\text{H}_5)_3$ (1.3 mmol) in anhydrous toluene (50 mL) at 120 °C for 12 h. After refluxing, the reaction mixture was filtered off, washed with hot anhydrous toluene and dried in vacuum at 40 °C over night to obtain “ $\text{C}_n\text{-SBA}$ ”. Then 3-aminopropyl (AP) groups were grafted on “ $\text{C}_n\text{-SBA}$ ” by refluxing 0.35 g (1.3 mmol) of 3-aminopropyl-triethoxysilane (APTES) in 50 mL anhydrous toluene to obtain “ $\text{C}_n\text{-AP-SBA}$ ”.

A series of catalysts having different alkyl-chain length was prepared by acidification

of C_n-AP-SBA using trifluoromethanesulfonic acid and ion exchange by decatungstate [Ref. S3]. Typically, 0.75 g of C_n-AP-SBA was mixed with 0.35 g (2.3 mmol) of CF₃SO₃H and stirred in 10 mL CH₂Cl₂ for 8 h, and then filtered off, washed with EtOH (15 mL), Ether (15 mL) respectively and dried in vacuum at room temperature for 3 h. The obtained powder was mixed with 0.78 g (0.3 mmol) of (n-Bu₄N)₄W₁₀O₃₂ in CH₃CN(15 mL) and stirred for 24 h. A straw yellow powder was filtered off, washed with CH₃CN until lacking of the typical UV-vis spectrum of the decatungstate (λ_{\max} =323 nm) for the washing filtrate, then washed with water (15 mL) and acetone (15 mL) respectively. Then the powder was dried in vacuum at room temperature over night to obtain W₁₀/ C_n-AP-SBA. The most active catalyst was W₁₀/ C₈-AP-SBA, and the final loading amount of W₁₀O₃₂⁴⁻ was 12 % (determined by ICP analysis).

1.2. Characterization of the catalysts

The textural structures were measured by N₂ adsorption at -196 °C in a Micromeritics TriStar ASAP 3000 system, and specific surface areas of samples were calculated using Brunauer–Emmett–Teller (BET) method. The pore size distributions (average pore diameter and mean pore volume) were measured from the N₂ desorption isotherm using the cylindrical pore model (BJH method). Transmission electron micrographs were obtained using a JEOL 2011 microscope operating at accelerating voltage of 200 kV. The samples for electron microscopy were prepared by dispersing the powder in ethanol and applying a drop of very dilute suspension on copper grids. The suspensions were dried by slow evaporation at ambient temperature. The FT-IR spectra were recorded at 25 °C with a Bruker Vector33 spectrophotometer (instrument) by mixing the catalyst and KBr. UV-vis diffuse reflectance spectra (UV-vis) were obtained with a UV-vis spectrophotometer (Shimadzu UV-2450) using BaSO₄ as the reference sample.

1.3. Catalytic procedure

1.3.1 Experiment apparatuses

The photoreactor was designed with a cylindrical quartz cell configuration (50 mL) and the suspension which in the photoreactor was surrounded by an external light source. The temperature of the suspension was maintained at 5-10 °C by water circulation through

an external cooling coil. The optical path-length was calculated 15 cm. The light source used was a 400 W high-pressure mercury lamp with a cutoff filter, cutting off wavelengths lower than 320 nm.

1.3.2 A typical procedure for photooxidation of alkanes

The heterocatalyst, substrate (1.7 mmol) and solvent (13 mL) were mixed and the suspension was stirred in the dark for 30 min with a 3 mL·min⁻¹ flow of O₂ to obtain a good dispersion, adsorption and a pure O₂ atmosphere (101.3 KPa). After irradiation, the sample was centrifuged, the products that remained absorbed on the irradiated powders were extracted three times with CH₂Cl₂ (3×2 mL); the filtrate was then analyzed by GC using a Agilent 6890 series instrument equipped with a flame ionization detector (FID) and a HP-5MS capillary column. The determination of hydroperoxides was performed by a spectrophotometric standard method reported in the literature [Ref. S4]. The loss of substrate during the reaction and analysis was <5 % for all experiments performed. The identification of the products was done in a GC-MS spectrometer comparing with commercially pure products.

1.3.3 Recovery and reuse of the hetero-catalysts

The catalyst was collected after filtration washed with acetone and heated at 80 °C for 12 h. Then the catalyst was used for next reaction.

[Ref. S1]: (a) D.Y. Zhao, Q.S. Huo, J.L. Feng, B. F. Chmelka, G. D. Stucky, *J. Am. Chem. Soc.* 1998, **120**, 6024; (b) D.Y. Zhao, J.L. Feng, Q.S. Huo, N. Melosh, G.H. Fredrickson, B.F. Chmelka, G.D. Stucky, *Science* 1998, **279**, 548.

[Ref. S2]: (a) B. Karimi, M. Ghoreishi-Nezhad, J.H. Clark, *Org. Lett.*, 2005, **7**, 625;
(b) R.Y. Zhang, W. Ding, B. Tu, D.Y. Zhao, *Chem. Mater.*, 2007, **19**, 4379;

[Ref. S3]: A. Molinari, G. Varani, E. Polo, S. Vaccari, A. Maldotti, *J. Mol. Catal. A: Chem.* 2007, **262**, 156.

[Ref. S4]: (a) A. Molinari, R. Amadelli, V. Carassiti, and A. Maldotti, *Eur. J. Inorg. Chem.*, 2000, 91; (b) R.D. Malr and A.J. Graupner, *Analy. Chem.*, 1964, **36**, 194.

2 Characterization results

2.1 UV-vis spectra of (A) $(\text{Bu}_4\text{N})_4\text{W}_{10}\text{O}_{32}$; (B) $\text{C}_8\text{-AP-SBA}$; (C) $\text{W}_{10}/\text{C}_8\text{-AP-SBA}$

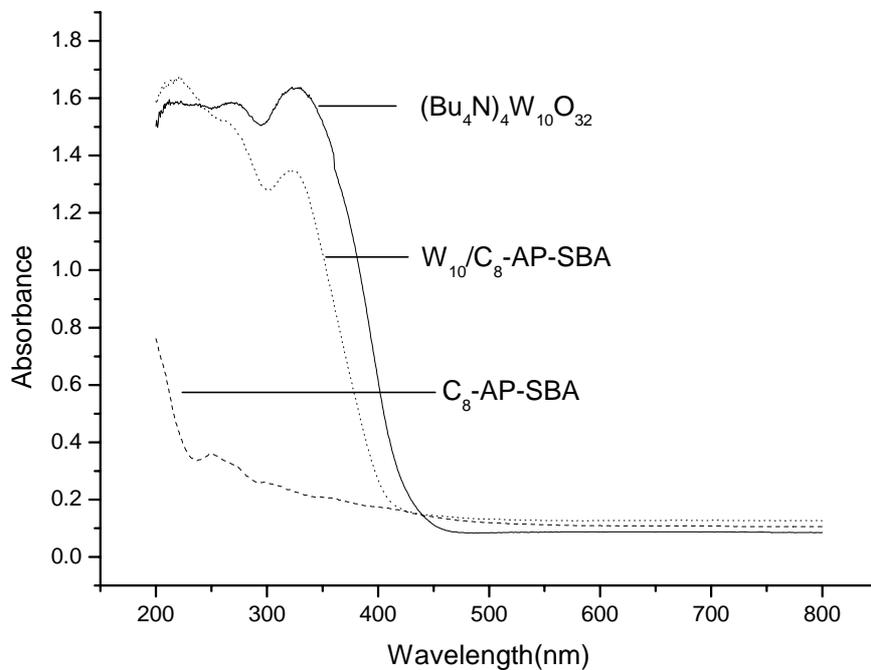


Fig S1

2.2 Physicochemical properties of the various functionalized catalysts and the SBA-15

Table S1

Sample	Surface area (m^2/g)	Pore volume (cm^3/g)	Pore size (nm)
SBA-15	757	1.26	6.7
AP-SBA	613	0.98	6.4
$\text{C}_8\text{-AP-SBA}$	461	0.68	5.9
$\text{W}_{10}/\text{AP-SBA}$	498	0.76	6.1
$\text{W}_{10}/\text{C}_2\text{-AP-SBA}$	439	0.65	5.9
$\text{W}_{10}/\text{C}_4\text{-AP-SBA}$	415	0.6	5.8
$\text{W}_{10}/\text{C}_8\text{-AP-SBA}$	376	0.53	5.6
$\text{W}_{10}/\text{C}_{16}\text{-AP-SBA}$	327	0.43	5.3

2.3 TEM image of catalyst W_{10}/C_8 -AP-SBA (A, B) before and (C, D) after reaction.

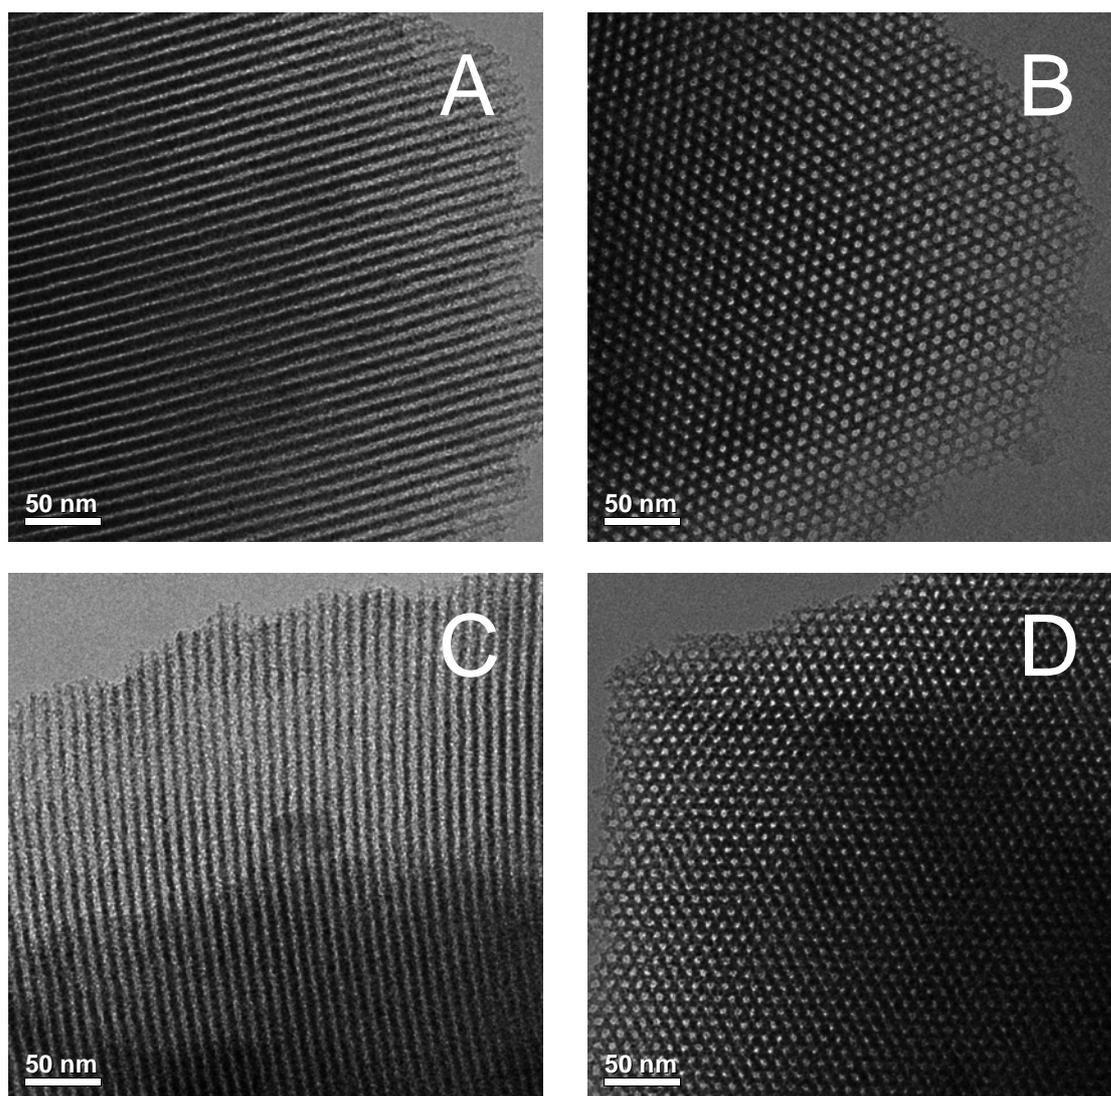


Fig S2

2.4 FT-IR spectra of (A) $(\text{Bu}_4\text{N})_4\text{W}_{10}\text{O}_{32}$; (B) SBA-15; (C) $\text{C}_8\text{-AP-SBA}$; (D) $\text{W}_{10}/\text{C}_8\text{-AP-SBA}$ before reaction; (E) $\text{W}_{10}/\text{C}_8\text{-AP-SBA}$ after reaction for 6 times

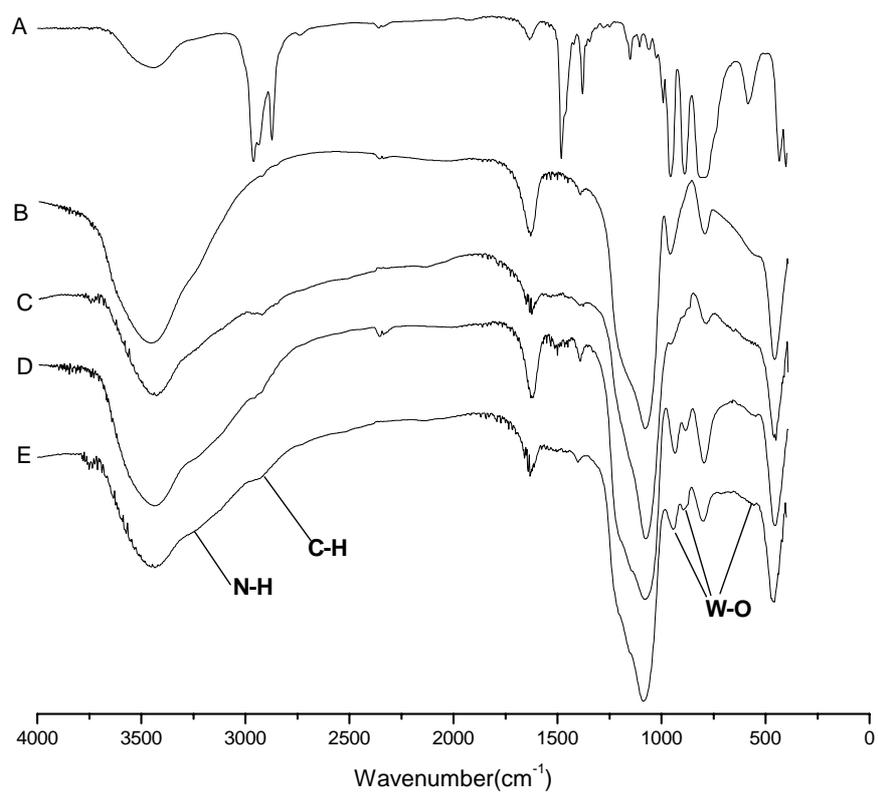


Fig S3

3 Photooxidation Reactions

3.1 O₂ photooxidation of ethylbenzene to acetophenone by (A) (Bu₄N)₄W₁₀O₃₂ in homogeneous and (B) W₁₀/C₈-AP-SBA in heterogeneous system using CH₃CN as solvent [black bars- mole fraction of 1-phenyl-ethylhydroperoxide in the photooxygenated products of ethylbenzene), grey bars- conversion (mol% ethylbenzene reacted)]

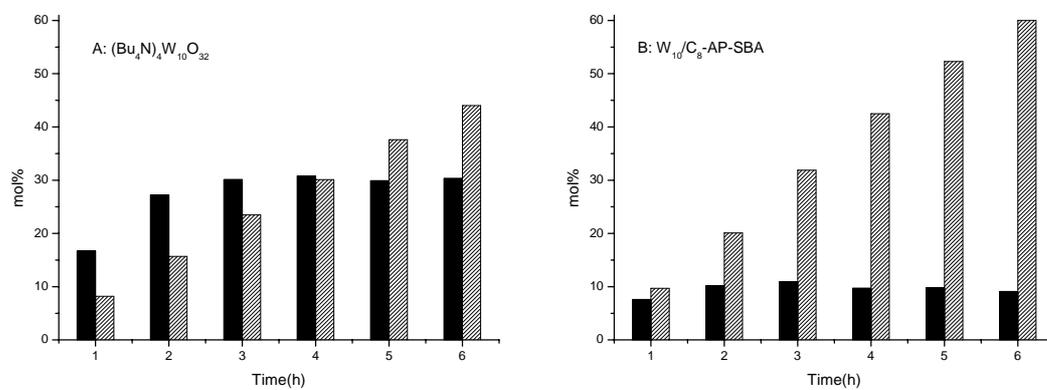


Fig S4

3.2 Comparison of photocatalytic activity and selectivity of decatungstate for ethylbenzene (Table S2) and cyclohexane (Table S3) oxygenation with different conditions used by different authors

Table S2.

Catalyst	Solvent	Reaction Time(h)	Major Product (Selectivity, mol%)	TOF(h ⁻¹)	Ref.
W ₁₀ /C ₈ -AP-SBA	CH ₃ CN/H ₂ O (1:1 v/v)	6	Acetophenone(96.5)	44	This work
(Bu ₄ N) ₄ W ₁₀ O ₃₂	CH ₃ CN	24	Acetophenone(76)	5	1
(Bu ₄ N) ₄ W ₁₀ O ₃₂ -Et ₃ SiH	CH ₃ CN	4	Acetophenone(84)	13	2
TBAW ₁₀ -HF	neat	4	Acetophenone(20) 1-Phenylethanol(66)	110	3
R _f NW ₁₀ -HF	neat	4	Acetophenone(38) 1-Phenylethanol(46)	861	3

1. D. Attanasio, L. Suber, K. Thorslund, *Inorg. Chem.*, 1991, **30**, 590.
2. I.N. Lykakis, M. Orfanopoulos, *Tetrahedron. Lett.*, 2004, **45**, 7645.
3. M. Carraro, M. Gardan, G. Scorrano, E. Orioli, E. Fontananova and M. Bonchio, *Chem. Commun.*, 2006, 4533.

Table S3.

Catalyst	Solvent	Reaction Time(h)	Major Product (Selectivity, mol%)	TOF(h ⁻¹)	Ref.
W ₁₀ /C ₈ -AP-SBA	CH ₃ CN/H ₂ O (1:1 v/v)	6	Cyclohexanone(97.5)	48	This work
(Bu ₄ N) ₄ W ₁₀ O ₃₂ /SiO ₂	CH ₂ Cl ₂	1.5	Cyclohexanone(50) Cyclohexanol(50)	16.5	1
(Et ₄ N) ₄ W ₁₀ O ₃₂ /SiO ₂	neat	4	Cyclohexanone(50) Cyclohexanol(50)	8.4	2
(Et ₃ NH) ₄ W ₁₀ O ₃₂ /SiO ₂	neat	4	Cyclohexanone(56.5) Cyclohexanol(43.5)	9.9	2
(Me ₄ N) ₄ W ₁₀ O ₃₂ /SiO ₂	neat	4	Cyclohexanone(54) Cyclohexanol(46)	9.6	2
(NH ₄) ₄ W ₁₀ O ₃₂ /SiO ₂	neat	4	Cyclohexanone(60) Cyclohexanol(40)	3	2
Na ₄ W ₁₀ O ₃₂ /SiO ₂	neat	4	Cyclohexanone(76) Cyclohexanol(24)	1.5	2
W30%/MCM-41	CH ₂ Cl ₂	2	Cyclohexanone(70) Cyclohexanol(30)	0.62	3

1. A.Molinari, R. Amadelli, L. Andreotti, A. Maldotti, *J. Chem. Soc. Dalton, Trans.*, 1999, 1203.
2. A.Molinari, R. Amadelli, A. Mazzacani, G. Sartori, A. Maldotti, *Langmuir.*, 2002, **18**, 5400.
3. A. Maldotti, A. Molinari, G. Varani, M. Lenarda, L. Storaro, F. Bigi, R. Maggi, A. Mazzacani and G. Sartori, *J. Catal.*, 2002, **209**, 210.